



Article

Annivite-(Zn), $\text{Cu}_6(\text{Cu}_4\text{Zn}_2)_{\Sigma 6}\text{Bi}_4\text{S}_{13}$, from the Jáchymov ore district, Czech Republic: the first Bi-dominant member of the tetrahedrite group

Jiří Sejkora^{1,2} , Cristian Biagioni³ , Zdeněk Dolníček¹, Dalibor Velebil¹ and Pavel Škácha^{1,4}

¹Department of Mineralogy and Petrology, National Museum, Cirkusová 1740, 193 00 Prague 9, Czech Republic; ²Earth Science Institute, Slovak Academy of Sciences, Dúbravská cesta 9, 840 05 Bratislava, Slovak Republic; ³Dipartimento di Scienze della Terra, Università di Pisa, Via Santa Maria, 53, I-56126 Pisa, Italy and ⁴Mining Museum Příbram, Hynka Kličky Place 293, 261 01 Příbram VI, Czech Republic

Abstract

Annivite-(Zn), $\text{Cu}_6(\text{Cu}_4\text{Zn}_2)_{\Sigma 6}\text{Bi}_4\text{S}_{13}$, is a new IMA-approved mineral species from the Geister vein, Jáchymov ore district, Czech Republic. It occurs as anhedral grains, up to 50 μm in size, and growth zones, up to 100 μm in thickness, hosted by oscillatory zoned annivite-(Zn)/tennantite-(Zn) grains, and associated with Bi-rich tennantite-(Zn), tennantite-(Fe), tetrahedrite-(Zn), the not-yet approved ‘annivite-(Fe)’, bismuth, emplectite, wittichenite and supergene bismite, walpurgite and metazeunerite. In reflected light, annivite-(Zn) is isotropic, pale grey with a brownish shade and very rare pale brown internal reflections. Reflectance data for the four COM wavelengths in air are [λ (nm): R (%)]: 470: 32.3; 546: 32.0; 589: 32.0; 650: 31.6. Electron microprobe analysis gave (in wt.% – average of 5 spot analyses): Cu 36.29, Ag 0.14, Fe 0.08, Zn 7.11, Pb 0.19, As 6.07, Sb 4.50, Bi 21.08, S 23.68, total 99.14. On the basis of $\Sigma \text{Me} = 16$ atoms per formula unit, the empirical formula of annivite-(Zn) is $\text{Cu}_{10.13}\text{Ag}_{0.02}\text{Zn}_{1.93}\text{Fe}_{0.03}\text{Pb}_{0.02}\text{Bi}_{1.79}\text{As}_{1.43}\text{Sb}_{0.66}\text{S}_{13.10}$. Annivite-(Zn) is cubic, $I\bar{4}3m$, with unit-cell parameters $a = 10.3545(6)$ Å, $V = 1110.16(19)$ Å³ and $Z = 2$. Its crystal structure was refined by single-crystal X-ray diffraction data to a final $R_1 = 0.0493$ on the basis of 278 unique reflections with $F_o > 4\sigma(F_o)$ and 23 refined parameters. Annivite-(Zn) is isotypic with other tetrahedrite-group minerals. Its crystal chemistry is discussed, and previous findings of Bi-rich tetrahedrite-group minerals are briefly reviewed, along with the description of a second finding of annivite-(Zn) from the abandoned Mauritius tin mine, Hřebečná, Krušné hory Mountains, Czech Republic.

Keywords: annivite-(Zn); new mineral; sulfosalt; tetrahedrite-group; copper; bismuth; crystal structure; Jáchymov; Czech Republic

(Received 27 April 2024; accepted 5 June 2024; Accepted Manuscript published online: 11 November 2024)

Introduction

Tetrahedrite-group minerals are the most common sulfosalts in different kinds of hydrothermal ore deposits. They form a complex isotypic series, with the general structural formula $M^{(2)}A_6^{M(1)}(B_4C_2)^{X(3)}D_4^{S(1)}Y_{12}^{S(2)}Z$, where $A = \text{Cu}^+$, Ag^+ , $\square$ (vacancy); $B = \text{Cu}^+$ and Ag^+ ; $C = \text{Zn}^{2+}$, Fe^{2+} , Hg^{2+} , Cd^{2+} , Ni^{2+} , Mn^{2+} , Cu^+ , In^{3+} and Fe^{3+} ; $D = \text{Sb}^{3+}$, As^{3+} , Bi^{3+} and Te^{4+} ; $Y = \text{S}^{2-}$ and Se^{2-} ; and $Z = \text{S}^{2-}$, Se^{2-} and $\square$. Thus, tetrahedrite-group minerals are characterised by several homo- and heterovalent substitutions. The classification of tetrahedrite-group minerals is based on the different combinations of chemical constituents, identifying distinct series according to different A, B, D and Y+Z constituents.

At the species level, the C chemical constituents are then considered (Biagioni *et al.*, 2020).

Among the currently known species, those having Sb ($Z = 51$) and As ($Z = 33$) as dominant D chemical constituents are the most widespread, whereas species with predominance of Te ($Z = 52$) are rare and those with Bi ($Z = 83$) are exceptional. The name annivite was formerly used to indicate the Bi-dominant analogue of tetrahedrite-group minerals. However, chemical analyses of type annivite from the Anniviers Valley (Switzerland – Fellenberg, 1854) corresponded to a Bi-rich variety of tennantite-(Fe). For this reason, annivite was considered as a questionable mineral (Moëlo *et al.*, 2008) and it was later discredited by Biagioni *et al.* (2020). However, some compositions corresponding to annivite are known (e.g. Lur’ye *et al.*, 1974, Bortnikov *et al.*, 1979; Kieft and Eriksson, 1984; Spiridonov *et al.*, 1986; Gołębiewska *et al.*, 2012; Velebil and Sejkora, 2018). According to Biagioni *et al.* (2020), annivite and its name could be re-validated if samples having isotypic relations with tetrahedrite-group minerals and showing $\text{Bi} > \text{As}$ and $\text{Bi} > \text{Sb}$ are found. This

Corresponding author: Jiří Sejkora; Email: jiri.sejkora@nm.cz

Associate Editor: David Hibbs

Cite this article: Sejkora J, Biagioni C, Dolníček Z, Velebil D and Škácha P (2025). Annivite-(Zn), $\text{Cu}_6(\text{Cu}_4\text{Zn}_2)_{\Sigma 6}\text{Bi}_4\text{S}_{13}$, from the Jáchymov ore district, Czech Republic: the first Bi-dominant member of the tetrahedrite group. *Mineralogical Magazine* 89, 102–112. <https://doi.org/10.1180/mgm.2024.54>

is the case described in this paper. In agreement with the current nomenclature of tetrahedrite-group minerals (Biagioni *et al.*, 2020), the hyphenated suffix ‘-(Zn)’ is added to the root-name ‘annivite’ in order to stress the dominance of Zn as C chemical constituent.

The new mineral and its name have been approved by the Commission on New Minerals, Nomenclature and Classification of the International Mineralogical Association, under the voting number IMA 2023–124 (Sejkora *et al.*, 2024). Its mineral symbol, in accord with Warr (2021), is Anv-Zn. Holotype material (polished section) of annivite-(Zn) is deposited in the collections of the Department of Mineralogy and Petrology, National Museum in Prague, Cirkusová 1740, 193 00 Praha 9, Czech Republic, under the catalogue number P1P 50/2023 whereas the grain used for single-crystal X-ray diffraction study (extracted from the above mentioned polished section) is kept in the collections of the Museo di Storia Naturale of the Università di Pisa, Via Roma 79, Calci (PI), under catalogue number 20069. This polished section was taken from the sample deposited in the collections of the Department of Mineralogy and Petrology, National Museum in Prague, under catalogue number P1N 39199.

Experimental

Occurrence and physical properties

Annivite-(Zn) was found on historical samples originally labelled ‘walpurgite’ or ‘tennantite’ originating from Jáchymov (St. Joachimsthal), Krušné hory Mountains, Czech Republic, which were stored in a mineralogical collection of the National Museum, Prague.

The Jáchymov ore district is a classic example of five element (Ag+As+Co+Ni+Bi) and U vein-type hydrothermal mineralisation (i.e. Kissin 1992; Markl *et al.*, 2016). The ore veins cut a complex of medium-grade metasedimentary rocks of Cambrian to Ordovician age, in the contact aureole of a Variscan granite pluton. The majority of the ore minerals was deposited during the Variscan mineralising epoch from mesothermal to epithermal fluids (Ondruš *et al.*, 2003a, 2003b, 2003d). Primary and supergene mineralisation in this district resulted in extraordinarily varied associations; more than 440 mineral species have been reported from there (Ondruš *et al.*, 1997a, 1997b and 2003c, 2003d; Hloušek *et al.*, 2014; Škácha *et al.*, 2019).

The type sample (P1N 39199) of annivite-(Zn) comes from the vein Geister, the 7th Geister level of the Rovnost I (Werner) shaft (GPS coordinates: 50°22′18.33″N, 12°53′32.79″E), western part of the Jáchymov ore district. The sample originally labelled ‘walpurgite’ (6 × 4 cm) is formed of a massive aggregate of ore composed of tetrahedrite-group minerals, emplectite and bismuth, and is partly supergene altered (bismite and walpurgite). The predominant mineral of the tetrahedrite group is Bi-rich tennantite-(Zn) accompanied by annivite-(Zn) and more rarely also Bi-rich tennantite-(Fe).

Annivite-(Zn) was also identified in other samples from the Geister vein with localisations 3rd Geister level (120 m under surface), 7th Geister level (232 m) and below Barbora level (262 m). All these samples probably come from one ore body of the Geister vein exposed in vertical extent at about 150 m; for a description of samples see Table S1 (Supplementary Material). The mineral association includes, in addition to the annivite-(Zn) proposed, Bi-rich tennantite-(Zn), tennantite-(Fe), tetrahedrite-(Zn), the

not-yet approved ‘annivite-(Fe)’, bismuth, emplectite, wittichenite and supergene bismite, walpurgite, arsenates of the vivianite group and metazeunerite. The occurrence of potential annivite-(Zn) at the Geister vein on the basis of electron microprobe data was previously mentioned by Velebil and Sejkora (2018). The tetrahedrite-group minerals form strongly chemically zoned aggregates and annivite-(Zn) only occurs as tiny growth zones and isometric domains (Fig. 1).

In holotype material, annivite-(Zn) occurs as anhedral grains, up to 50 µm in size, and growth zones (up to 100 µm in thickness) in zoned annivite-(Zn)/tennantite-(Zn) grains (Fig. 2). It is dark grey in colour, with a grey streak, and metallic lustre. Mohs hardness was not measured, but it should be close to 4, in agreement with other members of the tetrahedrite group. Annivite-(Zn) is brittle, with a conchoidal fracture and indistinct cleavage. Owing to the small amount of available material, density was not measured; based on the empirical formula and unit-cell parameters derived from single-crystal X-ray diffraction, the calculated density is 5.259 g/cm³. In reflected light, annivite-(Zn) is isotropic, pale grey, with brownish shade. Internal reflections are very rare in pale brown tints. Reflectance values (Table 1) were measured in air using a spectrophotometer MSP400 Tidas at Leica microscope, with a 50× objective and WTiC Zeiss 370 standard. These values are plotted in Fig. 3, whereas Fig. 4 compares them with published data for tennantite-(Zn) and tetrahedrite-(Zn).

Recently, annivite-(Zn) was also identified during the investigation of samples from dump material of the abandoned Mauritius mine. This tin mine is situated about 1 km N of the Hřebečná village, 16 km N of Karlovy Vary, Krušné hory Mountains, Czech Republic (GPS coordinates: 50°23′13.49″N, 12°49′51.72″E). The mineralisation studied, in coarse-grained quartz gangue with abundant fluorapatite, differs significantly from the usual fine-grained greisens mined in this area. The history, geology and mineralogy of the Hřebečná deposit can be found elsewhere (Jangl *et al.*, 1989; Urban, 2014; Sejkora *et al.*, 2021b). Annivite-(Zn) was determined in one sample of quartz gangue as anhedral domains 5–20 µm in size enclosed in grains of Bi-rich tennantite-(Zn) in close association with arsenopyrite and pyrite (Fig. 5). Other associated primary minerals are chalcopyrite, sphalerite, Cu sulfides (anilite, digenite, geerite, spionkopite and covellite), aikinite, bismuthinite, berryite, cuprobismutite, emplectite and wittichenite (Sejkora *et al.*, 2021b).

Chemical data

Quantitative chemical analyses on type material from Jáchymov and from the new finding at Hřebečná were carried out using a Cameca SX 100 electron microprobe (National Museum, Prague, Czech Republic) and the following experimental conditions: WDS mode, accelerating voltage 25 kV, beam current 20 nA and beam diameter 0.7 µm. Standards (element, emission line) were: Ag (AgLα), Bi₂Se₃ (BiMβ), chalcopyrite (CuKα and SKα), NiAs (AsLβ), PbS (PbMα), pyrite (FeKα), Sb₂S₃ (SbLα) and ZnS (ZnKα). The contents of other sought elements (Au, Cd, Co, Ga, Ge, Hg, In, Mn, Cl, Ni, Se, Sn, Te and Tl) were below detection limits. Matrix correction using the PAP procedure (Pouchou and Pichoir, 1985) was applied to the data. Analytical data for annivite-(Zn) from Jáchymov (average of 5 spot analyses) and Hřebečná (average of 8 spot analyses) are given in Table 2. The full dataset of EPMA data is deposited as Tables S2 and S3 (Supplementary Material).

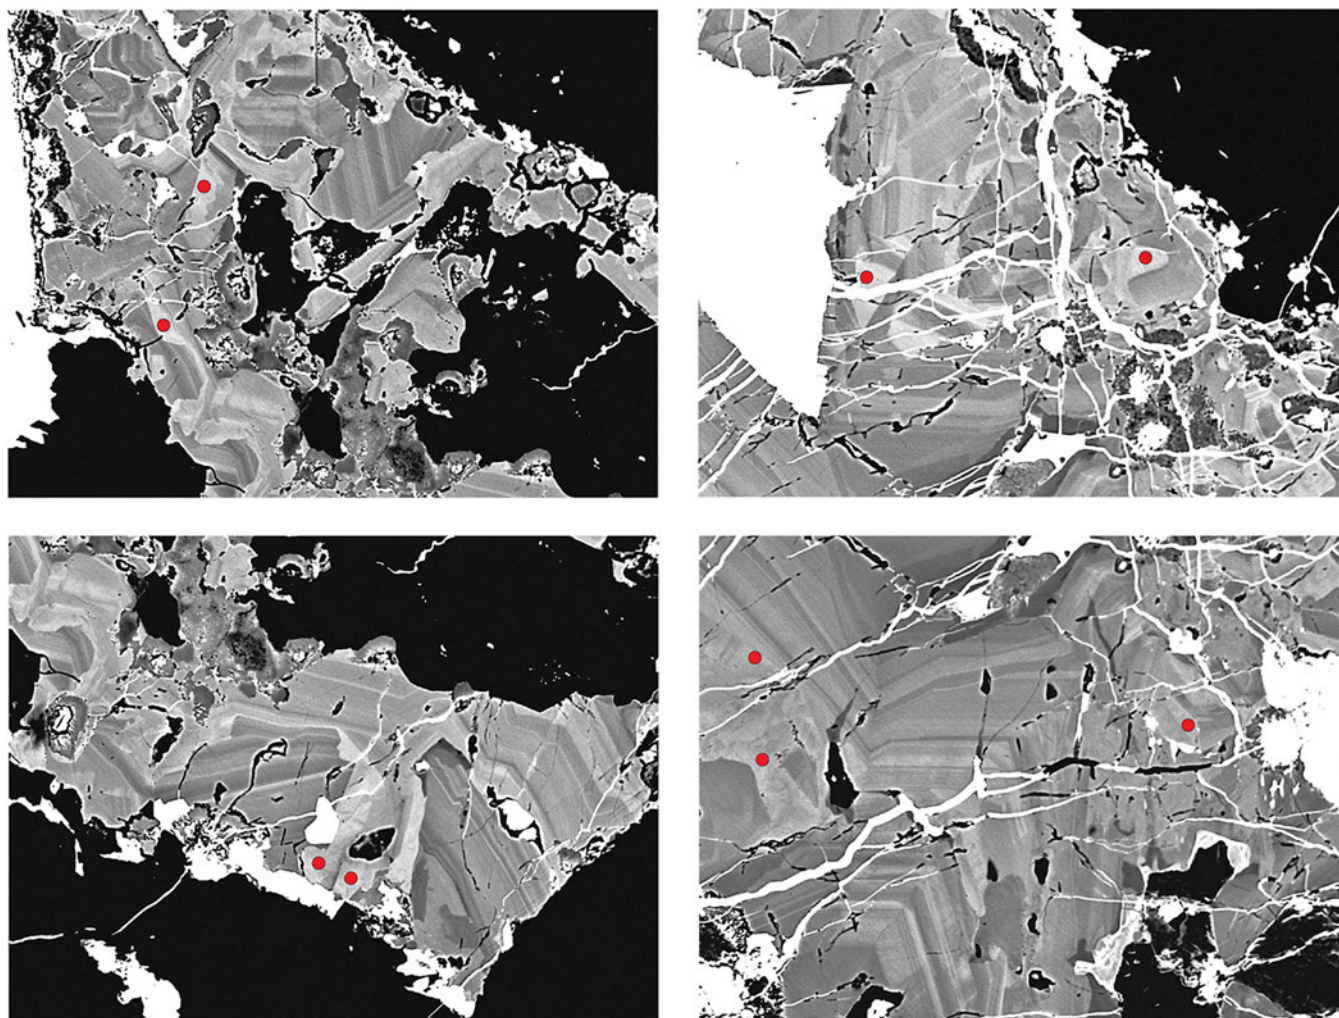


Figure 1. Back-scattered electron images of the chemically zoned grains of Bi-rich tennantite-(Zn) from the Geister vein, Jáchymov, Czech Republic, with zones and domains of annivite-(Zn) marked by red points; white is bismite and other supergene Bi and U minerals. Field of view of all images is 265 μm (sample P1N38896, National Museum Prague, image reproduced from Velebil and Sejkora, 2018).

X-ray crystallography

Powder X-ray diffraction data could not be collected, owing to the small amount of the available material. Consequently, these data, given in Table 3, were calculated through the software *PowderCell2.3* (Kraus and Nolze, 1996) using the structural model of the sample from Jáchymov discussed below.

Single-crystal X-ray diffraction intensity data were collected using a Bruker D8 Venture four-circle diffractometer equipped with an air-cooled Photon III detector, and microfocus MoK α radiation (Centro per l'Integrazione della Strumentazione scientifica dell'Università di Pisa, Università di Pisa, Italy). The detector-to-crystal distance was set to 38 mm. Data were collected using φ scan modes, in 0.5° slices, with an exposure time of 10 s per frame. A total of 560 frames were collected and they were integrated with the Bruker *SAINT* software package using a narrow-frame algorithm. Data were corrected for Lorentz-polarisation, absorption and background. Unit-cell parameters were refined on the basis of the XYZ centroids of 1652 reflections above $20\sigma I$ with $5.564^\circ < 2\theta < 62.73^\circ$ as $a = 10.3545(6)$ Å, $V = 1110.16(19)$ Å³ and space group *I43m*.

The crystal structure of annivite-(Zn) was refined using *Shelxl-2018* (Sheldrick, 2015) starting from the atomic coordinates of Johnson and Burnham (1985). The occurrence of a racemic twin was modelled. The following neutral scattering curves, taken from the *International Tables for Crystallography* (Wilson, 1992) were used: Cu vs. $\square$ (vacancy) at the *M*(2) and *M*(1) sites; Bi vs. As at *X*(3); and S at the *S*(1) and *S*(2) sites. The site occupancies at the *M*(2) and *M*(1) positions did not deviate from full occupancy by Cu and were fixed to one; taking into account the similarity of site scattering between Cu ($Z = 29$) and Zn ($Z = 30$), the latter replacing Cu at the *M*(1) site, their ratio was fixed in accord with electron microprobe data. After several cycles of isotropic refinement, the R_1 converged to 0.0868, confirming the correctness of the structural model. The anisotropic model for both cations and anions converged to $R_1 = 0.0555$. Residuals were located around the *M*(2) and *X*(3) sites, suggesting their possible splitting. Allowing the splitting of these positions, the structural model converged to $R_1 = 0.0493$ for 278 reflections with $F_o > 4\sigma(F_o)$ and 23 refined parameters. Details of data collection and refinement are given in Table 4. Fractional atom coordinates and equivalent isotropic displacement parameters are reported in Table 5. Table 6 reports

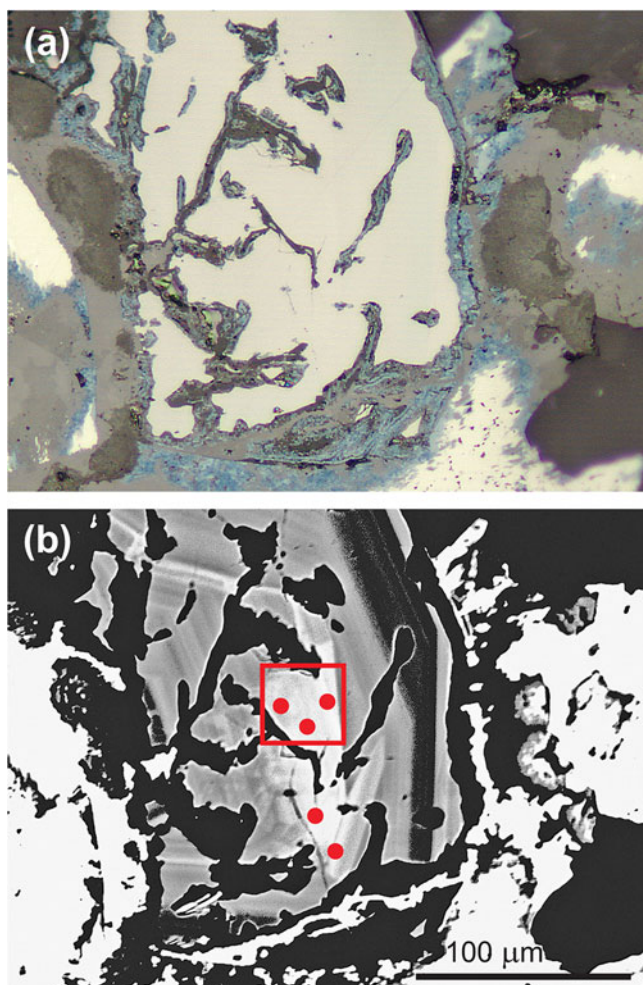


Figure 2. Reflected light (a) and back-scattered electron (b) images of the chemically zoned crystal of tetrahedrite-group minerals (TGM). The white domain marked by red points within the grain of TGM corresponds to annivite-(Zn). The grain used from single-crystal X-ray diffraction study was extracted from the red box. Holotype sample (polished section) P1P 50/2023; this polished section was taken from hand-size sample P1N39199, National Museum Prague.

Table 1. Reflectance data for annivite-(Zn) from Jáchymov, Czech Republic

λ (nm)	R (%)	λ (nm)	R (%)
400	33.6	560	32.0
420	33.4	580	32.0
440	33.1	589	32.0
460	32.5	600	32.1
470	32.3	620	31.9
480	32.2	640	31.8
500	32.1	650	31.6
520	32.0	660	31.5
540	31.9	680	31.1
546	32.0	700	30.4

Note: the four COM values are shown in bold.

selected bond distances, whereas weighted bond-valence sums, calculated according to Brese and O'Keeffe (1991), are shown in Table 7. The crystallographic information file has been deposited with the Principal Editor of *Mineralogical Magazine* and is available as Supplementary material (see below).

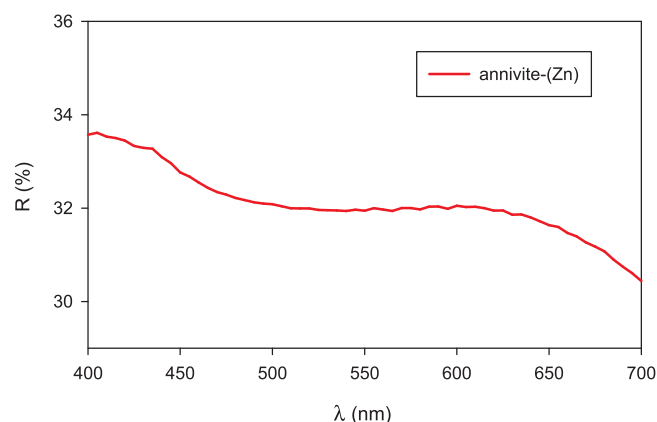


Figure 3. Reflectance curve for annivite-(Zn) from Jáchymov, Czech Republic.

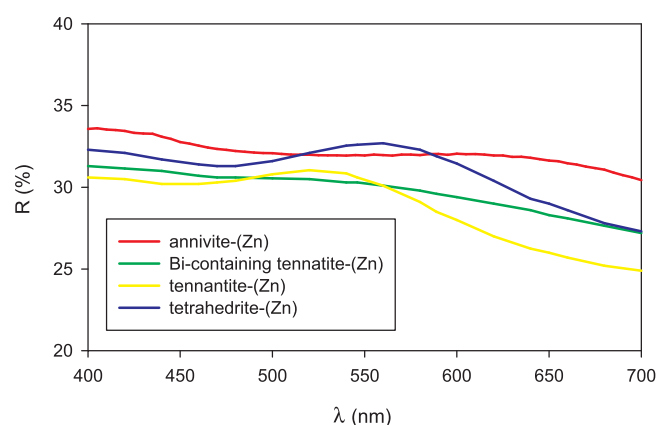


Figure 4. Reflectance curve for annivite-(Zn) from Jáchymov, Czech Republic (this paper) compared with published data for tennantite-(Zn) with 0.56 apfu Bi from Bicknoller Quarry, Somerset, UK (Criddle and Stanley, 1993); tennantite-(Zn) from Tsumeb (Criddle and Stanley, 1993) and tetrahedrite-(Zn) from Fresney d'Oisans, Isère, France (Criddle and Stanley, 1993).

Results and discussion

Chemical formula

As discussed in previous papers (e.g. Sejkora *et al.*, 2021a), there are different approaches to recalculate the chemical formulae of tetrahedrite-group minerals. The two better ones normalise the number of atoms on the basis of $\Sigma Me = 16$ atoms per formula unit (apfu) or on the basis of $(As + Sb + Te + Bi) = 4$ apfu. The former approach assumes that no vacancies occur at the $M(2)$, $M(1)$, and $X(3)$ sites, whereas the latter is based mainly on the results discussed by Johnson *et al.* (1986) who revealed that negligible variations in the ideal number of atoms hosted at the $X(3)$ position usually occur.

The first approach gives the chemical formulae $Cu_{10.13}Ag_{0.02}Zn_{1.93}Fe_{0.03}Pb_{0.02}(Bi_{1.79}As_{1.43}Sb_{0.66})_{\Sigma 3.88}S_{13.10}$ (holotype material from Jáchymov) and $Cu_{9.87}Ag_{0.02}Zn_{1.85}Fe_{0.34}(Bi_{1.91}As_{1.72}Sb_{0.30})_{\Sigma 3.93}S_{13.34}$ (Hřebečná) whereas the other normalisation strategy corresponds to the formulae $Cu_{10.44}Ag_{0.02}Zn_{1.99}Fe_{0.03}Pb_{0.02}(Bi_{1.84}As_{1.48}Sb_{0.68})_{\Sigma 4.00}S_{13.50}$ (holotype Jáchymov) and $Cu_{10.05}Ag_{0.02}Zn_{1.89}Fe_{0.34}(Bi_{1.95}As_{1.75}Sb_{0.30})_{\Sigma 4.00}S_{13.60}$ (Hřebečná). The simplified formula of annivite-(Zn) is $(Cu,Ag)_6(Cu,Zn,Fe,Pb)_6(Bi,As,Sb)_4S_{13}$ corresponding to the

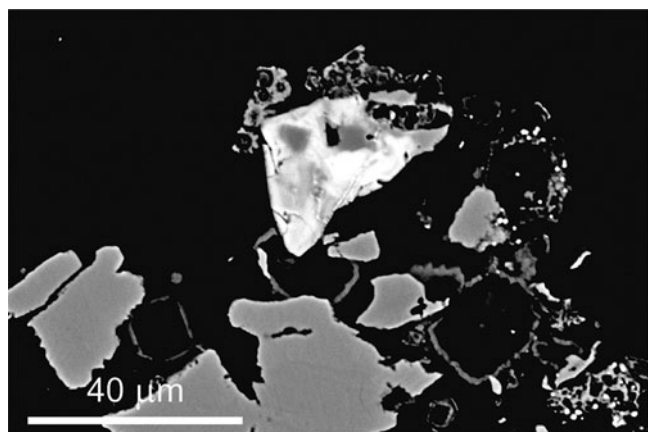


Figure 5. Back-scattered electron image of annivite-(Zn) domains (white) hosted in a zonal aggregate of Bi-rich tennantite-(Zn) in association with arsenopyrite (grey) and pyrite (black); Hřebečná, Czech Republic.

end-member formula $\text{Cu}_6(\text{Cu}_4\text{Zn}_2)_5\text{Bi}_4\text{S}_{13}$. This corresponds to (in wt.%) Cu 31.48, Zn 6.48, Bi 41.40, S 20.64, total 100.00.

Chemical variability of Bi-rich members of the tetrahedrite group from Jáchymov and Hřebečná

The composition for all studied samples of Bi-rich members of the tetrahedrite group from the Geister vein, Jáchymov are shown in Figs 6 and 7 (based on $\Sigma\text{Me} = 16$ apfu, Table S2). Tennantite-(Zn) is the most common (345 spot analyses) and shows a wide range of Bi contents (0.43–1.86 apfu) accompanied by dominant As (1.53–3.07 apfu) and subordinate Sb (up to 0.95 apfu). The C chemical constituent is dominated by Zn ranging between 0.93–2.02 apfu. There are 171 spot analyses that correspond to annivite-(Zn) with dominant Bi (1.54–2.37 apfu) accompanied by As (0.87–1.83 apfu) and Sb (0.09–1.10 apfu); the Zn contents range between 0.98 and 2.00 apfu. We also observed thin (5–10 μm) zones (16 spot analyses) with chemical composition corresponding to the not-yet approved ‘annivite-(Fe)’ with dominant Bi contents in the range 1.58–1.98 apfu and Fe (0.93–1.16 apfu) prevailing over Zn (0.68–0.94 apfu). Relatively abundant (67 spot analyses) tennantite-(Fe) shows, in addition to the dominant As (1.61–2.67 apfu), also elevated Bi (0.50–1.74 apfu) and Sb (0.02–1.06 apfu) contents; Fe content ranges between 0.94 and 1.42 apfu. The Bi-rich (0.80–1.20 apfu) tetrahedrite-(Zn) was found only rarely in

the samples studied (9 spot analyses). For all the studied members of the tetrahedrite group, the (Cu + Ag) content is very close to the ideal one, i.e. 10.00 apfu, ranging between 9.81 and 10.31 apfu, whereas Ag contents are negligible (up to 0.16 apfu). The C chemical constituent is represented by dominant Zn or Fe; however, Zn is clearly more abundant than Fe, and compositions close to Fe end-members were not detected (Fig. 7a,b). Minor Pb (locally up to 0.54 apfu) is here also considered as a C constituent, even if its actual structural role in tetrahedrite-group minerals is currently unknown (e.g. Biagioni *et al.*, 2024). The contents of Bi distinctly correlate negatively with As contents (Fig. 7c), on the contrary, no correlations were found between Bi-Sb, As-Sb, Fe-Bi, Fe-As, Pb-Bi, Pb-Sb and Pb-Fe.

Annivite-(Zn) from Hřebečná is much rarer (Fig. 8, Table S3) and displays Bi contents between 1.85–2.20 apfu (8 spot analyses); the most abundant tennantite-(Zn) with 0.05–1.73 apfu Bi (143 spot analyses) is accompanied by rare tennantite-(Fe) with 0.05–1.32 Bi (10 spot analyses). All members of the tetrahedrite group from Hřebečná are poorer in Sb than the Jáchymov ones (Fig. 8), as the observed contents reached up 0.36 Sb apfu only. The contents of Ag are negligible (up to 0.07 apfu); the dominant C-cation is mainly Zn, and Fe is present only in sporadic cases, accompanied in a part of the analyses by some formally divalent Cu (up to 0.77 apfu).

Crystal structure description

The crystal structure of annivite-(Zn) agrees with the general features of the members of the tetrahedrite isotypic group. The electron density associated with the $M(2)$ site is split into two subpositions, i.e. $M(2a)$ and $M(2b)$, with $M(2a)-M(2b) = 0.53(4)$ Å. The former has a triangular coordination, whereas the latter has a flat trigonal pyramidal coordination. Average $\langle M(2a)-S \rangle$ and $\langle M(2b)-S \rangle$ distances are 2.256 and 2.31 Å. The refinement of the site occupancy points to a pure Cu site, in agreement with electron microprobe data indicating a negligible amount of Ag. The bond-valence sum, i.e. 1.04 valence units (vu), is in accord with such an occupancy by formally monovalent Cu.

The tetrahedrally coordinated $M(1)$ site has an average $\langle M(1)-S \rangle$ bond distance of 2.339 Å, similar to those reported by Wuensch (1964) and Wuensch *et al.* (1966) for tetrahedrite-(Fe/Zn) and tennantite-(Zn), i.e. 2.342 and 2.337 Å, respectively. Electron microprobe analysis indicates that it has an ideal $(\text{Cu}_{0.67}\text{Zn}_{0.33})$ site occupancy. On the basis of

Table 2. Chemical data (in wt.%) for annivite-(Zn) from Jáchymov (grain used for single crystal X-ray diffraction study) and Hřebečná, in the Czech Republic

Constituent	Jáchymov ($n = 5$)			Hřebečná ($n = 8$)		
	mean	range	(σ)	mean	range	(σ)
Cu	36.29	35.75–36.68	0.34	35.33	34.69–35.84	0.40
Ag	0.14	0.11–0.20	0.04	0.11	0.08–0.16	0.03
Fe	0.08	0.05–0.13	0.04	1.06	1.00–1.15	0.05
Zn	7.11	6.92–7.24	0.12	6.82	6.70–6.92	0.07
Pb	0.19	0.00–0.37	0.13	0.00		
As	6.07	5.10–6.95	0.68	7.26	6.64–7.82	0.34
Sb	4.50	3.07–5.54	0.91	2.02	1.58–2.49	0.39
Bi	21.08	19.81–22.47	0.98	22.48	21.60–23.47	0.76
S	23.68	23.34–23.91	0.22	24.10	23.86–24.40	0.20
Total	99.14	99.00–99.30	0.11	99.19	98.31–100.30	0.65

(σ) – estimated standard deviation; n = number of spot analyses.

Table 3. Calculated X-ray powder diffraction data for annivite-(Zn)*

I_{calc}	d_{calc}	$h\ k\ l$	I_{calc}	d_{calc}	$h\ k\ l$
7	5.177	2 0 0	7	2.031	4 3 1
3	4.227	2 1 1	6	1.890	5 2 1
12	3.661	2 2 0	40	1.830	4 4 0
100	2.989	2 2 2	3	1.776	4 3 3
8	2.767	3 2 1	7	1.680	6 1 1
22	2.589	4 0 0	3	1.680	5 3 2
9	2.441	4 1 1	2	1.637	6 2 0
3	2.315	4 2 0	20	1.561	6 2 2
3	2.208	3 3 2	3	1.527	6 3 1
3	2.114	4 2 2	3	1.495	4 4 4
2	2.031	5 1 0			

*Relative intensity and d_{hkl} (Å) were calculated using the software PowderCell2.3 (Kraus and Nolze, 1996) on the basis of the structural model given in Tables 4 and 5. Only reflections with $I_{\text{calc}} > 2$ are listed. The five strongest reflections are given in bold.

Table 4. Crystal and experimental data for annivite-(Zn) from Jáchymov, Czech republic

Crystal data	
Crystal size (mm)	0.050 × 0.040 × 0.040
Cell setting, space group	Cubic, $I\bar{4}3m$
a (Å)	10.3545(6)
V (Å ³)	1110.16(19)
Z	2
Data collection and refinement	
Radiation, wavelength (Å)	MoK α , $\lambda = 0.71073$
Temperature (K)	293(2)
$2\theta_{\text{max}}$ (°)	56.39
Measured reflections	1770
Unique reflections	278
Reflections with $F_o > 4\sigma(F_o)$	278
R_{int}	0.0790
$R\sigma$	0.0362
Range of h, k, l	$-13 \leq h \leq 13$ $-9 \leq k \leq 13$ $-13 \leq l \leq 12$
$R [F_o > 4\sigma(F_o)]$	0.0493
R (all data)	0.0493
wR (on F_o^2) ¹	0.1291
Goof	1.166
Absolute structure parameter ²	0.37(7)
Number of least-squares parameters	23
Maximum and minimum residual peak (e Å ⁻³)	1.92 [at 0.47 Å from $M(2a)$] -1.14 [at 2.03 Å from $M(1)$]

¹ $w = 1/[\sigma^2(F_o^2) + (0.0521P)^2 + 67.1698P]$.

²Flack (1983).

this proposed site occupancy, the bond-valence sum at the $M(1)$ site is 1.40 vu, to be compared with a theoretical value of 1.33 vu.

The $X(3)$ site was found to be split into two sub-positions, separated by a distance of 0.29(3) Å. The $X(3a)$ sub-site has a $\langle X(3a)-S \rangle$ distance of 2.477 Å, whereas the $X(3b)$ has an average bond distance of 2.330 Å. Refined site scattering at the $X(3a) + X(3b)$ site corresponds to 55.00 electrons per site. The site occupancy, based on electron microprobe data, would be $(\text{Bi}_{0.448}\text{As}_{0.358}\text{Sb}_{0.165}\square_{0.029})$, corresponding to a mean atomic number of 57.41 electrons. Observed bond distances suggest that $X(3a)$

Table 5. Site, site occupancy (s.o.), fractional atom coordinates and equivalent isotropic displacement parameters (Å²) for annivite-(Zn)

Site	s.o.	x/a	y/b	z/c	U_{eq}
$M(2a)$	$\text{Cu}_{0.66(6)}$	0.2167(10)	0	0	0.023(6)
$M(2b)$	$\text{Cu}_{0.17(3)}$	0.222(3)	-0.036(2)	0.036(2)	0.023(6)
$M(1)$	$\text{Cu}_{0.67}\text{Zn}_{0.33}$	1/4	1/2	0	0.0238(16)
$X(3a)$	$\text{Bi}_{0.44(2)}$	0.2748(5)	0.2748(5)	0.2748(5)	0.0144(16)
$X(3b)$	$\text{As}_{0.56(2)}$	0.2589(13)	0.2589(13)	0.2589(13)	0.0144(16)
$S(1)$	$\text{S}_{1.00}$	0.1167(4)	0.1167(4)	0.3598(6)	0.0186(15)
$S(2)$	$\text{S}_{1.00}$	0	0	0	0.019(4)

Table 6. Selected bond distances (in Å) for annivite-(Zn)

$M(1)-S(1)$	×4	2.339(4)	$M(2a)-S(2)$	2.244(10)
			$M(2a)-S(1)$	×2 2.262(9)
$X(3a)-S(1)$	×3	2.477(8)		
$X(3b)-S(1)$	×3	2.330(12)	$M(2b)-S(1)$	×2 2.286(19)
			$M(2b)-S(2)$	2.36(3)

is a mixed (Bi,As) position whereas $X(3b)$ is a mixed (As,Sb) position. On the basis of the observed average bond distances, one can calculate the ratios for Bi/As and As/Sb. The ideal As-S and Sb-S distances can be calculated on the basis of bond parameters of Brese and O'Keeffe (1991) and correspond to 2.26 and 2.45 Å, respectively; these values are close to those observed for As-S (2.246 Å) and Sb-S (2.446 Å) bonds by Wuensch *et al.* (1966) and Wuensch (1964), respectively. Some comments are necessary for the Bi-S ideal bond in trigonal pyramidal coordination. By using the bond parameters of Brese and O'Keeffe (1991), the ideal Bi-S value of 2.55 Å can be calculated. However, in some species showing trigonal-pyramidally coordinated Bi, the Bi-S is longer, e.g. 2.61 Å in empetite (Kyono and Kimata, 2005), and 2.592 Å in wittichenite (Kocman and Nuffield, 1973). Moreover, the results of Klünder *et al.* (2003) indicated a possible maximum Bi-S bond length of 2.511 Å in tetrahedrite-group minerals. As the observed unit-cell parameters for the sample studied agree with the trend expected for Bi-bearing tetrahedrite-group minerals, as suggested by these latter authors, we used their proposed Bi-S distance of 2.51 Å (only two digits are considered). The Bi/As and As/Sb ratios at $X(3a)$ and $X(3b)$, calculated on the basis of these ideal bond distances, are 0.88/0.12 and 0.63/0.37. Considering these ratios and the refined site scatterings at $X(3a)$ (= 36.52 electrons) and $X(3b)$ (= 18.48 electrons), one achieves the site occupancies $(\text{Bi}_{0.42}\text{As}_{0.06})$ and $(\text{As}_{0.29}\text{Sb}_{0.17})$, resulting in an occupancy at $X(3a) + X(3b)$ of $(\text{Bi}_{0.42}\text{As}_{0.35}\text{Sb}_{0.17}\square_{0.06})$, in accord with chemical data. On the basis of the proposed site occupancies, the bond-valence sum at $X(3a) + X(3b)$ is 2.97 vu.

The $S(1)$ and $S(2)$ sites are fully occupied by S. Their bond-valence sums are 1.97 and 1.86 vu, respectively.

The structural formula of annivite-(Zn), based on electron microprobe data and crystal structure refinement, assuming that no vacancy occurs at the $X(3)$ site, could be written as $M(2)\text{Cu}_{6.00}M(1)(\text{Cu}_{4.00}\text{Zn}_{2.00})_{\Sigma 6.00}X(3)(\text{Bi}_{1.80}\text{As}_{1.48}\text{Sb}_{0.72})_{S(1)+S(2)}S_{13.00}$ ($Z = 2$).


Relationship between Bi content and unit-cell parameter

The results of electron microprobe analysis, $(\text{Cu}_{6.11}\text{Ag}_{0.02})_{\Sigma 6.13}(\text{Cu}_{4.02}\text{Zn}_{1.93}\text{Fe}_{0.03}\text{Pb}_{0.02})_{\Sigma 6.00}(\text{Bi}_{1.79}\text{As}_{1.43}\text{Sb}_{0.66})_{\Sigma 3.88}S_{13.10}$, as well as the structural analysis, suggest the possible simplified formula

Table 7. Weighted bond-valence sums (in valence units) in annivite-(Zn)*

Site	M(1)	M(2a)	M(2b)	X(3a)	X(3b)	Σ anions	Theoretical
S(1)	$2x \rightarrow 0.33 \times 4 \downarrow$	$0.22 \times 2 \downarrow$	$2x \rightarrow 0.05 \times 2 \downarrow$	$0.51 \times 3 \downarrow$	$0.48 \times 3 \downarrow$	1.97	2.00
S(2)		$6x \rightarrow 0.23$	$12x \rightarrow 0.04$			1.86	2.00
Σ cations	1.32	0.67	0.14	1.53	1.44		
Theoretical	1.00	0.66	0.17	1.53	1.38		

*Note: bond-valence sums were weighted according to the site occupancies discussed in the text and using the bond parameters of Brese and O'Keeffe (1991). Left and right superscripts indicates bonding involving cations and anions, respectively.

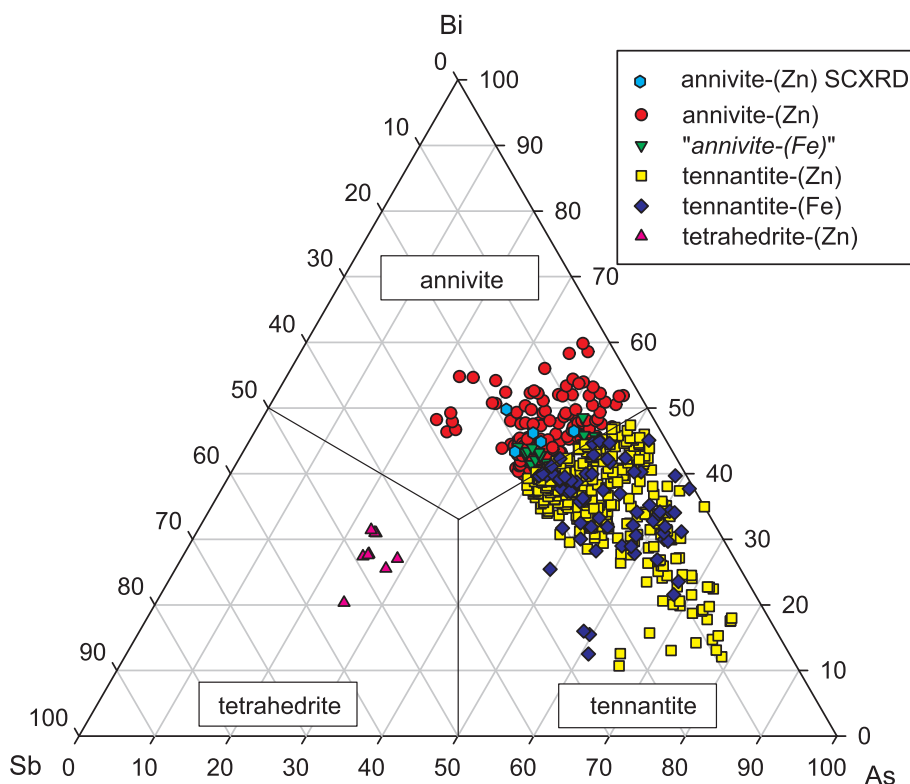**Figure 6.** Ternary Bi-Sb-As diagram (at.%) for tetrahedrite-group minerals from the Geister vein, Jáchymov, Czech Republic.

$\text{Cu}_6(\text{Cu}_4\text{Zn}_2)(\text{Bi}_{1.8}\text{As}_{1.5}\text{Sb}_{0.7})\text{S}_{13}$. This formula can be used for calculating the expected unit-cell parameter of the sample studied.

Johnson *et al.* (1987) proposed the following relation between the unit-cell parameter a and the chemistry of the sample studied: a (Å) = $10.379 + 0.082(\text{Ag}) - 0.01(\text{Ag}^2) - 0.009(\text{Cu}^*) + 0.066(\text{Hg}) - 0.038(\text{As}) + 0.144(\text{Bi})$. On the basis of the simplified formula given above, the calculated unit-cell parameter a would be 10.59 Å, very different from the observed value of 10.35 Å. Indeed, Johnson *et al.* (1987) stated that the data for Bi used in their regression equation were anomalous, limiting the usefulness of the Bi term in their equation. If the data of synthetically prepared Bi-rich members (Klunder *et al.*, 2003) are used to derive the new coefficient for Bi in the Johnson *et al.* (1987) formula, the value 0.0075(Bi) is found; for this coefficient the calculated unit-cell parameter for the composition of type material is $a = 10.34$ Å, which corresponds very well to the observed value of 10.35 Å.

Another approach is that of Klunder *et al.* (2003) who proposed an increase in the a unit-cell parameter of 0.036 Å for every Bi atom in tennantite and 0.011 Å in tetrahedrite. As the studied sample is a mixed (As/Sb) term, the composition $\text{Cu}_6(\text{Cu}_4\text{Zn}_2)(\text{As}_{3.3}\text{Sb}_{0.7})\text{S}_{13}$, that is with all Bi replaced by As, could be initially used. According to the relation of Johnson *et al.* (1987), this composition should have the unit-cell parameter $a = 10.25$ Å; following Charlat and

Lévy (1975), the a value should be 10.26 Å. Considering the occurrence of 1.8 Bi apfu, the unit-cell should increase to ~ 10.32 Å, to be compared with the observed value of 10.35 Å.

Bismuth in tetrahedrite-group minerals

A survey of the available literature reveals that Bi-dominant members of tetrahedrite-group have been reported since the end of the 1970s. They have been mentioned from five occurrences (Table 8): Vindfall, Sweden with 2.26 apfu Bi (Kieft and Eriksson, 1984); Tary-Ekan, Central Asia with 1.57 apfu Bi (Lur'ye *et al.*, 1974; Bortnikov *et al.*, 1979; Spiridonov *et al.*, 1986); Rędziny, Poland with 2.65 apfu Bi (Gołębiewska *et al.*, 2012); Jáchymov (Velebil and Sejkora, 2018) and Hřebečná, both Czech Republic (Sejkora *et al.*, 2021b). The material from Jáchymov and Hřebečná was newly investigated and is the subject of this paper. Other published chemical compositions (e.g. Oen and Kieft, 1976; Sergeyeva and Shatagin, 1980; Vinogradova *et al.*, 1985; Igumnova, 1986; Borisova *et al.*, 1986; Förster *et al.*, 1986; Dobosi and Nagy, 1991; Breskova and Tarkian, 1994 and references therein; Kemkina, 2007; Voudouris *et al.*, 2008; Staude *et al.*, 2010) correspond, in fact, to Bi-rich tennantite-, tetrahedrite- or goldfieldite-series minerals, respectively.

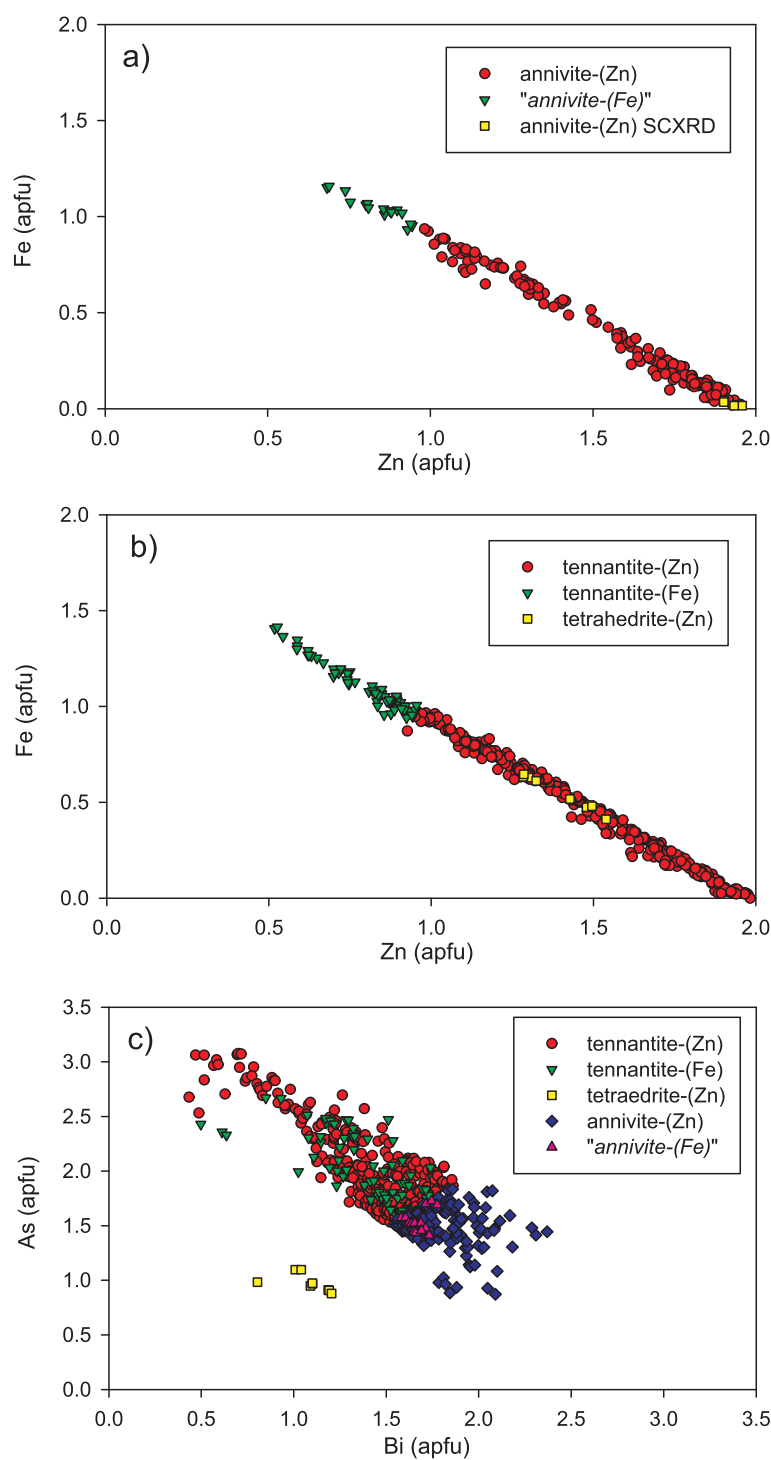


Figure 7. Compositional variations Zn vs. Fe (in apfu) of Bi-bearing tetrahedrite-group minerals from the Geister vein, Jáchymov, Czech Republic. (a) Zn vs. Fe (in apfu) for Bi-dominant members; (b) Zn vs. Fe (in apfu) for As- and Sb-dominant members; (c) Bi vs. As (in apfu).

It is worth noting that among samples of 'annivite' given in Table 8, arsenic is usually more abundant than Sb, with As/(As+Sb) atomic ratios between 0.54 and 0.87. The only sample with Sb > As, having As/(As+Sb) = 0.13, has a high Ag content (3.41 Ag apfu). It is possible that the small As atoms and the large Bi atoms may approximate together the size of the Sb atoms, thus favouring the solubility of Bi in As-rich members of tetrahedrite group. On the contrary, the substitution of Sb by Bi could cause an expansion of the crystal structure of tetrahedrite-group minerals, balanced by the introduction of the large Ag atoms replacing

Cu. However, synthetic experiments do not fully support this hypothesis.

Indeed, attempts to synthesise a Bi-dominant analogue of tetrahedrite or tennantite have not yet been successful; Klünder *et al.* (2003) report Bi contents in synthetically prepared tetrahedrites and tennantites up to 0.8 apfu at 350°C and up to 1 apfu at 450 and 520°C, but no meaningful differences between Sb- and As-rich phases were observed. The synthetic Bi-doped members of tetrahedrite group were prepared many times for studies of their promising thermoelectric properties but with maximum Bi

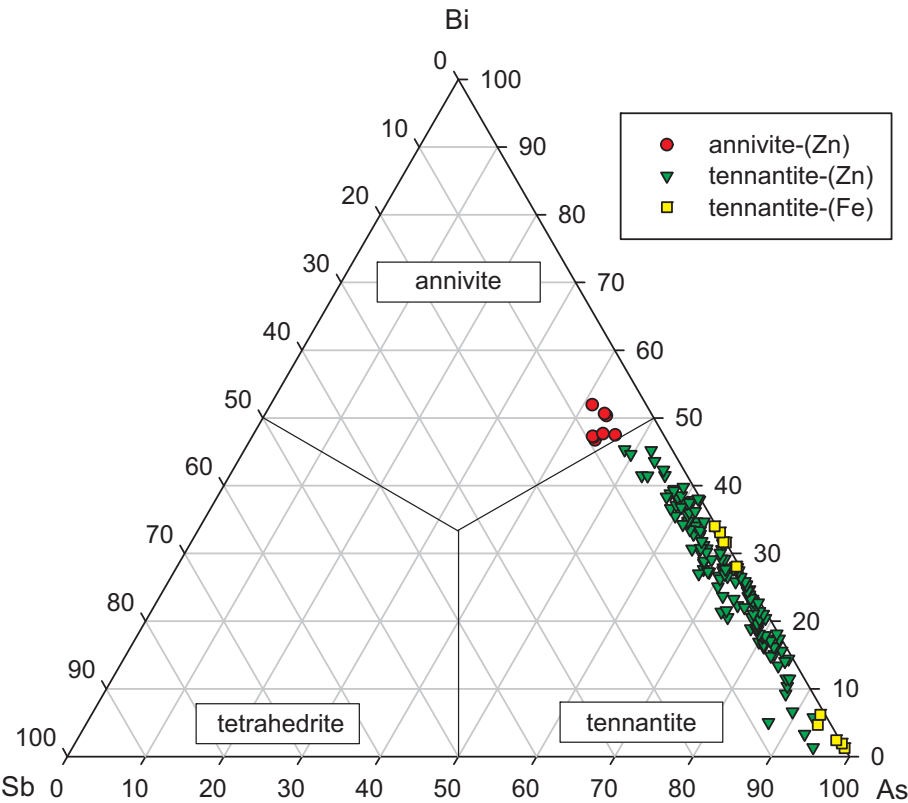


Figure 8. Ternary Bi-Sb-As diagram (at.%) for tetrahedrite-group minerals from the Hřebečná deposit, Czech Republic.

Table 8. Published data for Bi-dominant members of tetrahedrite group, recalculated on the basis of $\Sigma Me = 16$

Occurrence	Reference	Empirical formula
Vindfall	Kieft and Eriksson (1984)	Bi content 2.64 apfu, Zn-dominant*
Tary-Ekan	Lur’ye et al. (1974)	$Cu_{9.08}Ag_{0.95}Zn_{1.76}(Bi_{1.57}As_{1.43}Sb_{1.21})\Sigma_{4.21}S_{12.51}$
Rędziny	Gołębiowska et al. (2012)	$Cu_{6.88}Ag_{3.41}Fe_{1.89}(Bi_{2.65}Sb_{1.02}As_{0.15})\Sigma_{3.82}(S_{12.60}Se_{0.01})\Sigma_{12.61}$
Jáchymov	Velebil and Sejkora (2018)	$Cu_{10.15}Ag_{0.03}Zn_{1.14}Fe_{0.82}(Bi_{1.89}As_{1.69}Sb_{0.25})\Sigma_{3.83}S_{13.91}$
Hřebečná	Sejkora et al. (2021b)	$Cu_{9.89}Ag_{0.02}Zn_{1.86}Fe_{0.33}(Bi_{2.02}As_{1.61}Sb_{0.27})\Sigma_{3.90}S_{13.62}$

*Chemical analysis is not given; sample from Rędziny corresponds to the not-yet approved ‘argentoannivite-(Fe)’; other samples are annivite-(Zn)

content of 0.80 apfu (Kumar et al., 2017; Peccerillo and Durose, 2018).

Conclusion

Annivite-(Zn) is a new member of the tetrahedrite group. Its discovery and comparison with other members of this group confirm the fundamental role of studies devoted to natural mineral assemblages to reveal novel crystal structures so far not obtained in synthesis experiments (e.g. Klünder et al., 2003).

Moreover, tetrahedrite-group minerals are currently actively studied for their high-tech properties (e.g. Suekuni et al., 2014; Chetty et al., 2015; Levinsky et al., 2019). Among the chemical compositions showing interesting properties, synthetic Bi-doped members have potential thermoelectric properties which have been the subject of several research works in the last decade (e.g. Goncalves et al., 2016; Kumar et al., 2017; Peccerillo and Durose, 2018; Kwak et al., 2020; Lee and Kim, 2020; Baláž et al., 2021).

Supplementary material. The supplementary material for this article can be found at <https://doi.org/10.1180/mgm.2024.54>.

Acknowledgements. We appreciate the many constructive comments of an anonymous reviewer, Panagiotis Voudouris, Peter Leverett, the Associate Editor and Principal Editor Stuart Mills that helped to improve this paper significantly. The study was supported financially by the Ministry of Culture of the Czech Republic (long-term project DKRVO 2024-2028/1.II.a; National Museum, 00023272) and by the Slovak Research and Development Agency under the contract APVV-22-0041. CB acknowledges the financial support by the Ministero dell’Istruzione, dell’Università e della Ricerca through the project PRIN 2017 “TEOREM – deciphering geological processes using Terrestrial and Extraterrestrial ORE Minerals”, prot. 2017AK8C32. The Centro per l’Integrazione della Strumentazione scientifica dell’Università di Pisa (C.I.S.U.P.) is thanked for the access to the single-crystal X-ray diffraction laboratory.

Competing interests. The authors declare none.

References

Baláž P., Guilmeau E., Achimovičová M., Baláž M., Daneu N., Dobrozhan O. and Kaňuchová M. (2021) Bismuth doping in nanostructured tetrahedrite: Scalable synthesis and thermoelectric performance. *Nanomaterials*, **11**, 1386.
Biagioni C., George L.G., Cook N.J., Makovicky E., Moëlo Y., Pasero M., Sejkora J., Stanley C.J., Welch M.D. and Bosi F. (2020) The tetrahedrite group: Nomenclature and classification. *American Mineralogist*, **105**, 109–122.

- Biagioni C., Voudouris P., Moëlo Y., Sejkora J., Dolníček Z., Musetti S., and Mauro D. (2024) Crystal structure of Pb-bearing watanabeite from Pefka, Greece. *Mineralogical Magazine*, **88**, 218–227, [10.1180/mgm.2024.14](https://doi.org/10.1180/mgm.2024.14).
- Borisova E.A., Borodaev Y.S. and Bocharova G.I. (1986) Rare types of tetrahedrite-tennantite ores of a gold ore deposit. *Zapiski Vsesoyuznogo Mineralogicheskogo Obshchestva*, **115**, 63–72 [in Russian].
- Bortnikov N.S., Kudryavtsev A.S. and Troneva N.V. (1979) Bi-rich tetrahedrite from the Tary-Ekan deposit (East Karamazar, Central Asia). *Mineralogicheskij Zhurnal*, **198**, 61–64 [in Russian].
- Brese N.E. and O'Keeffe M. (1991) Bond-valence parameters for solids. *Acta Crystallographica*, **B47**, 192–197.
- Breskovska V. and Tarkian M. (1994) Composition variation in Bi-bearing fahlores. *Neues Jahrbuch für Mineralogie, Monatshefte*, **1994**, 230–240.
- Charlat M. and Lévy C. (1975) Influence des principales substitutions sur le paramètre cristallin de la série tennantite-tétraédrite. *Bulletin de la Société française de Minéralogie et Cristallographie*, **98**, 152–158.
- Chetty R., Bali A. and Mallik R.C. (2015) Tetrahedrites as thermoelectric materials: an overview. *Journal of Materials Chemistry C*, **3**, 12364–12378.
- Criddle A.J. and Stanley C.J. (1993) *Quantitative Data File for Ore Minerals*. Third edition. Chapman & Hall, London.
- Dobosi G. and Nagy B. (1991) Contributions to the mineralogy of the Lahóca hydrothermal ore deposits of Recsk, North-Hungary. *Annual Report of the Hungarian Geological Survey*, **1991**, 289–320.
- Fellenberg L.R. (1854) Über ein eigenthümliches Fahlerz aus dem Einfischthale in Kanton Wallis. *Mittheilungen der Naturforschenden Gesellschaft in Bern*, **317–318**, 57–59.
- Flack H.D. (1983) On enantiomorph-polarity estimation. *Acta Crystallographica*, **A39**, 876–881.
- Förster H.-J., Hunger H.-J. and Grimm L. (1986) Elektronenstrahlmikroanalytische Untersuchungen von Erzmineralen aus Zinn-Lagerstätte Altenberg (Erzgebirge, DDR). Mitteilung: Fahlerze – Chemismus und Nomenklatur. *Chemie der Erde*, **47**, 111–115.
- Golebiewska B., Pieczka A. and Parafiniuk J. (2012) Substitution of Bi for Sb and As in minerals of the tetrahedrite series from Rędziny, Lower Silesia, southwestern Poland. *The Canadian Mineralogist*, **50**, 267–279.
- Goncalves A., Lopes E., Villeroy B., Monnier J., Godart C. and Lenoir B. (2016) Effect of Ni, Bi and Se on the tetrahedrite formation. *RSC Advances*, **6**, 102359–102367.
- Hloušek J., Plášil J., Sejkora J. and Škácha P. (2014) News and new minerals from Jáchymov, Czech Republic (2003–2014). *Bulletin mineralogicko-petrologického oddělení Národního muzea v Praze*, **22**, 155–181 [in Czech].
- Igumnova N.S. (1986) New isomorphous series: tennantite-goldfieldite-annivite. *Zapiski Vsesoyuznogo Mineralogicheskogo Obshchestva*, **115**, 449–454 [in Russian].
- Jangl L., Hašková K. and Lisková S. (1989) *Rolava-Hřebečná, part Hřebečná*. Unpublished report, Geofond, Kutná Hora GKH 235 [in Czech].
- Johnson M.L. and Burnham C.W. (1985) Crystal structure refinement of an arsenic-bearing argentian tetrahedrite. *American Mineralogist*, **70**, 165–170.
- Johnson N.E., Craig J.R. and Rimstidt J.D. (1986) Compositional trends in tetrahedrite. *The Canadian Mineralogist*, **24**, 385–397.
- Johnson N.E., Craig J.R. and Rimstidt J.D. (1987) Effect of substitutions on the cell dimension of tetrahedrite. *The Canadian Mineralogist*, **25**, 237–244.
- Kemkina R.A. (2007) Fahlores of the Prasolovka Au-Ag volcanogenic deposit, Kunashir Island, Russian Far East. *Russian Journal of Pacific Geology*, **1**, 130–143.
- Kieft K. and Eriksson G. (1984) Regional zoning and metamorphic evolution of the Vindfall Pb-Zn ore, east central Sweden. *Geologiska Föreningens i Stockholm Förhandlingar*, **106**, 305–317.
- Kissin S.A. (1992) Five-element (Ni-Co-As-Ag-Bi) veins. *Geoscience Canada*, **19**, 113–124.
- Klinder M.H., Karup-Møller S. and Makovicky E. (2003) Exploratory studies on substitutions in the tetrahedrite-tennantite solid solution series. III. The solubility of bismuth in tetrahedrite-tennantite containing iron and zinc. *Neues Jahrbuch für Mineralogie, Monatshefte*, **2003**, 153–175.
- Kocman V. and Nuffield E.W. (1973) The crystal structure of wittichenite, Cu_3BiS_3 . *Acta Crystallographica*, **B29**, 2528–2535.
- Kraus W. and Nolze G. (1996) POWDER CELL – a program for the representation and manipulation of crystal structures and calculation of the resulting X-ray powder patterns. *Journal of Applied Crystallography*, **29**, 301–303.
- Kumar D.S.P., Chetty R., Femi O.E., Chattopadhyay K., Malar P. and Mallik R.C. (2017) Thermoelectric properties of Bi doped tetrahedrite. *Journal of Electronic Materials*, **46**, 2616–2622.
- Kwak S.G., Pi J.H., Lee G.E. and Kim I.H. (2020) Solid-state synthesis and thermoelectric properties of tetrahedrites $\text{Cu}_{12}\text{Sb}_{4-y}\text{Bi}_y\text{S}_{13}$. *Korean Journal of Metals and Materials*, **58**, 272–277.
- Kyono A. and Kimata M. (2005) Crystal structures of chalcostibite (CuSbS_2) and emplectite (CuBiS_2): Structural relationship of stereochemical activity between chalcostibite and emplectite. *American Mineralogist*, **90**, 162–165.
- Lee G.E. and Kim I.H. (2020) Effects of Zn/Bi double doping on the charge transport and thermoelectric properties of tetrahedrites $\text{Cu}_{12-x}\text{Zn}_x\text{Sb}_{4-y}\text{Bi}_y\text{S}_{13}$. *Journal of Electronic Materials*, **49**, 2768–2774.
- Levinsky P., Candolfi C., Dauscher A., Tobola A., Hejtmánek J. and Lenoir B. (2019) Thermoelectric properties of the tetrahedrite – tennantite solid solutions $\text{Cu}_{12}\text{Sb}_{4-x}\text{As}_x\text{S}_{13}$ and $\text{Cu}_{10}\text{Co}_2\text{Sb}_{4-y}\text{As}_y\text{S}_{13}$ ($0 \leq x, y \leq 4$). *Physical Chemistry Chemical Physics*, **21**, 4547–4555.
- Lur'ye L.M., Tsepin A.I. and Vyal'sov L.N. (1974) Properties of composition of fahlores from the Tary-Ekan deposit (Eastern Karamazar, Central Asia). *Geologiya Rudnykh Mestorozhdeniy*, **16**, 65–70 [in Russian].
- Markl G., Burisch M. and Neumann U. (2016) Natural fracturing and the genesis of five-element veins. *Mineralium Deposita*, **51**, 703–712.
- Moëlo Y., Makovicky E., Mozgova N.N., Jambor J.L., Cook N., Pring A., Paar W.H., Nickel E.H., Graeser S., Karup-Møller S., Balić-Žunić T., Mumme W.G., Vurro F., Topa D., Bindi L., Bente K. and Shimizu M. (2008) Sulfosalt systematics: a review. Report of the sulfosalt sub-committee of the IMA Commission on Ore Mineralogy. *European Journal of Mineralogy*, **20**, 7–46.
- Oen I.S. and Kieft C. (1976) Bismuth-rich tennantite and tetrahedrite in the Mangualde pegmatite, Viseu district, Portugal. *Neues Jahrbuch für Mineralogie, Monatshefte*, **1976**, 94–96.
- Ondruš P., Veselovský F., Hloušek J., Skála R., Frýda J., Čejka J. and Gabašová A. (1997a) Secondary minerals of the Jáchymov (Joachimsthal) ore district. *Journal of the Czech Geological Society*, **42**, 3–76.
- Ondruš P., Veselovský F., Skála R., Císařová I., Hloušek J., Frýda J., Vavřín I., Čejka J. and Gabašová A. (1997b) New naturally occurring phases of secondary origin from Jáchymov (Joachimsthal). *Journal of the Czech Geological Society*, **42**, 77–107.
- Ondruš P., Veselovský F., Gabašová A., Drábek M., Dobeš P., Malý K., Hloušek J. and Sejkora J. (2003a) Ore-forming processes and mineral parageneses of the Jáchymov ore district. *Journal of the Czech Geological Society*, **48**, 157–192.
- Ondruš P., Veselovský F., Gabašová A., Hloušek J. and Šrein V. (2003b) Geology and hydrothermal vein system of the Jáchymov (Joachimsthal) ore district. *Journal of the Czech Geological Society*, **48**, 3–18.
- Ondruš P., Veselovský F., Gabašová A., Hloušek J. and Šrein V. (2003c) Supplement to secondary and rock-forming minerals of the Jáchymov ore district. *Journal of the Czech Geological Society*, **48**, 149–155.
- Ondruš P., Veselovský F., Gabašová A., Hloušek J., Šrein V., Vavřín I., Skála R., Sejkora J. and Drábek M. (2003d) Primary minerals of the Jáchymov ore district. *Journal of the Czech Geological Society*, **48**, 19–147.
- Peccerillo E. and Durose K. (2018) Copper-antimony and copper-bismuth chalcogenides—Research opportunities and review for solar photovoltaics. *MRS Energy & Sustainability*, **5**, E13.
- Pouchou J.L. and Pichoir F. (1985) “PAP” ($\varphi\rho Z$) procedure for improved quantitative microanalysis. Pp. 104–106 in: *Microbeam Analysis* (J.T. Armstrong, editor). San Francisco Press, San Francisco.
- Sejkora J., Biagioni C., Vrtiška L. and Moëlo Y. (2021a) Zvěstovite-(Zn), $\text{Ag}_6(\text{Ag}_4\text{Zn}_2)\text{As}_4\text{S}_{13}$, a new tetrahedrite-group mineral from Zvěstov, Czech Republic. *Mineralogical Magazine*, **85**, 716–724.
- Sejkora J., Pauliš P., Urban M., Dolníček Z., Ulmanová J. and Pour O. (2021b) Mineralogy of quartz veins of the tin deposit Hřebečná near Abertamy in Krusné hory Mountains (Czech Republic). *Bulletin Mineralogie Petrologie*, **29**, 131–163 [in Czech].
- Sejkora J., Biagioni C., Dolníček Z., Velebil D. and Škácha P. (2024) Annivite-(Zn), IMA 2023-124. CNMNC Newsletter 79, *Mineralogical Magazine*, **88**, [10.1180/mgm.2024.45](https://doi.org/10.1180/mgm.2024.45)

- Sergeyeva N.E. and Shatagin N.N. (1980) On the bismuth mineralization of the Yubileino–Shegirikhinskii deposit (Rudnyi Altai). *Doklady Akademii Nauk SSSR*, **252**, 959–962 [in Russian].
- Sheldrick G.M. (2015) Crystal structure refinement with SHELXL. *Acta Crystallographica*, **C71**, 3–8.
- Škacha P., Plášil J. and Horák V. (2019) *Jáchymov: mineralogická perla Krušnohoří*. Academia, Praha 682 pp. [in Czech].
- Spiridonov E.M., Chvileva T.N., Borodaev Yu.S., Vinogradova R.A. and Kononov O.V. (1986) The influence of bismuth on optical properties of gray copper. *Doklady Akademii Nauk SSSR*, **290**, 1475–1478 [in Russian].
- Staude S., Mordhorst T., Neumann R., Prebeck W. and Markl G. (2010) Compositional variation of the tennantite–tetrahedrite solid-solution series in the Schwarzwald ore district (SW Germany): the role of mineralization processes and fluid source. *Mineralogical Magazine*, **74**, 309–339.
- Suekuni K., Tomizawa Y., Ozaki T. and Koyano M. (2014) Systematic study of electronic and magnetic properties for $\text{Cu}_{12-x}\text{TM}_x\text{Sb}_4\text{S}_{13}$ (TM= Mn, Fe, Co, Ni, and Zn) tetrahedrite. *Journal of Applied Physics*, **115**, 143702.
- Urban M. (2014) *Mining Towns of Krušné hory Mountains. Part 1 Karlovy Vary Region*. 317 pp. Fornica publishing, Sokolov, Czech Republic [in Czech].
- Velebil D. and Sejkora J. (2018) Bi-rich tennantites from Jáchymov (Czech Republic). *Bulletin Mineralogie Petrologie*, **26**, 213–222 [in Czech].
- Vinogradova R.A., Kononov O.V., Borodayev Y.S., Bochek L.I. and Dvortsova S.P. (1985) Bismuth-bearing fahlore of the Tyrnyauz. *Zapiski Vsesoyuznogo Mineralogicheskogo Obshchestva*, **140**, 340–344 [in Russian].
- Voudouris P., Melfos V., Spry P.G., Bonsall T.A., Tarkian M. and Solomos C. (2008) Carbonate-replacement Pb–Zn–Ag±Au mineralization in the Kamariza area, Lavrion, Greece: Mineralogy and thermochemical conditions of formation. *Mineralogy and Petrology*, **94**, 85–106.
- Warr L.N. (2021) IMA-CNMNC approved mineral symbols. *Mineralogical Magazine*, **85**, 291–320.
- Wilson A.J.C. (editor) (1992) *International Tables for Crystallography Volume C: Mathematical, Physical and Chemical Tables*. Kluwer Academic Publishers, Dordrecht, The Netherlands.
- Wuensch B.J. (1964) The crystal structure of tetrahedrite, $\text{Cu}_{12}\text{Sb}_4\text{S}_{13}$. *Zeitschrift für Kristallographie*, **119**, 437–453.
- Wuensch B.J., Takéuchi Y. and Nowacki W. (1966) Refinement of the crystal structure of binnite, $\text{Cu}_{12}\text{As}_4\text{S}_{13}$. *Zeitschrift für Kristallographie*, **123**, 1–20.